

VANADIS 6 SUPERCLEAN³

High performance powder metallurgical cold work tool steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

Critical tool steel parameters for

GOOD TOOL PERFORMANCE

- Correct hardness for the application
- Very high wear resistance
- High toughness to prevent premature failure due to chipping/crack formation.

High wear resistance is often associated with low toughness and vice-versa. However, in many cases both high wear resistance and toughness are essential for optimal tooling performance.

Vanadis 6 is a powder metallurgical cold work tool steel offering a combination of very high wear resistance and good toughness.

TOOLMAKING

- Machinability
- Heat treatment
- Dimensional stability in heat treatment
- Surface treatment.

Toolmaking with highly alloyed tool steels means that machining and heat treatment have to be considered more than with lower alloyed grades. This can, of course, raise the cost of toolmaking.

Due to the very carefully balanced alloying and the powder metallurgical manufacturing route, Vanadis 6 has a similar hardening procedure as the common cold work tool steels. In order to reduce the amount of retained austenite and to optimize the abrasive wear resistance high temperature tempering is recommended. One very big advantage with Vanadis 6 is that the dimensional stability after hardening and tempering is much better than for conventionally produced cold work steels and HSS used for cold work. This also means that Vanadis 6 is a tool steel which is very suitable for CVD and PVD coating.

Applications

Vanadis 6 is suitable for long run tooling of work materials where mixed (abrasive–adhesive) or abrasive wear and/or chipping/cracking and/or plastic deformation are dominating failure mechanisms.

Examples:


- Blanking and fine blanking of harder work materials
- Forming operations where a high compressive strength is essential
- Powder compacting
- Substrate steel for surface coating
- Plastics moulds and tooling subjected to abrasive wear conditions
- Knives.

General

Vanadis 6 is a chromium-molybdenum-vanadium alloyed PM steel which is characterized by:

- Very high abrasive-adhesive wear resistance
- High compressive strength
- Good toughness
- Very good dimensional stability at heat treatment and in service
- Very good through-hardening properties
- Good resistance to tempering back
- High cleanliness.

Typical analysis %	C 2,1	Si 1,0	Mn 0,4	Cr 6,8	Mo 1,5	V 5,4
Delivery condition	Soft annealed to approx. 255 HB					
Colour code	Green/Dark green					

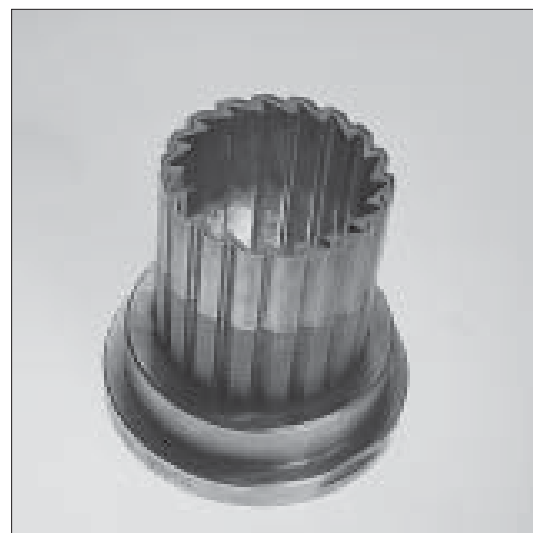

Powder pressing punch of Vanadis 6. Excellent results have been obtained for compacting iron powder when abrasive wear reduced the punch life. (Courtesy GKN Sinter Metals AB, Kolsva.)

Properties

PHYSICAL DATA

Hardened and tempered to 60 HRC.


Temperature	20°C (68°F)	200°C (390°F)	400°C (750°F)
Density, kg/m ³ lbs/in ³	7 610 0,27	– –	– –
Modulus of elasticity MPa psi	225 000 32,6 x 10 ⁶	210 000 30,4 x 10 ⁶	190 000 27,5 x 10 ⁶
Coefficient of thermal expansion per °C from 20°C °F from 68°F	– –	11,2 x 10 ⁻⁶ 6,2 x 10 ⁻⁶	12,0 x 10 ⁻⁶ 6,7 x 10 ⁻⁶
Thermal conductivity W/m • °C Btu in/(ft ² h °F)	– –	22 154	25 175
Specific heat capacity J/kg °C Btu/lb°F	460 0,110	– –	– –

IMPACT STRENGTH


Approximate room temperature impact strength at different tempering temperatures.

Specimen size: 7 x 10 x 55 mm (0,27 x 0,40 x 2,2") unnotched. Hardened at 1050°C (1920°F).

Quenched in air. Tempered 2 x 2h.

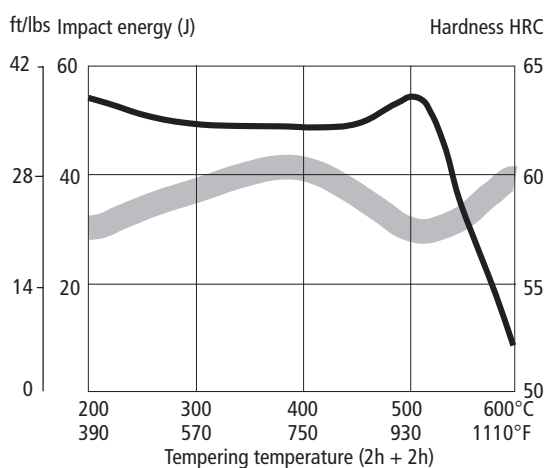

Approximate room temperature impact strength for Vanadis 4 Extra, Vanadis 6 and Vanadis 10 at 62 HRC. Short transverse direction. High temperature tempered condition

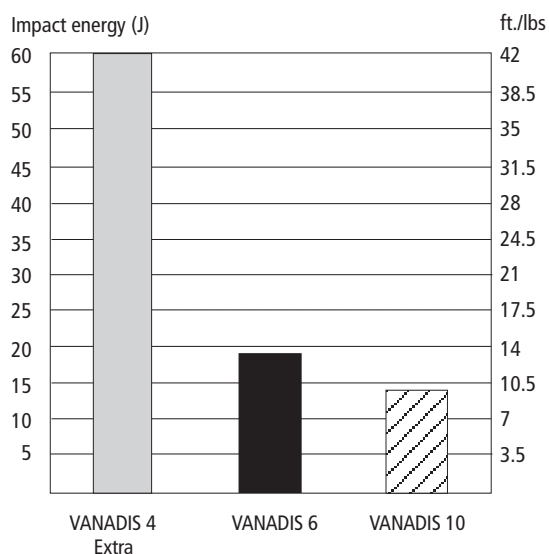


COMPRESSIVE STRENGTH

Hardness	Compressive strength Rc0,2
60 HRC	2 290 MPa
62 HRC	2 530 MPa
64 HRC	2 760 MPa

High temperature tempered, 525°C (977°F) 2 + 2h.

WEAR RESISTANCE

Pin on disc test. Disc material SiO₂. Hardness is 62 HRC for all steels. High temperature tempered condition. Low value is equivalent to good wear resistance.

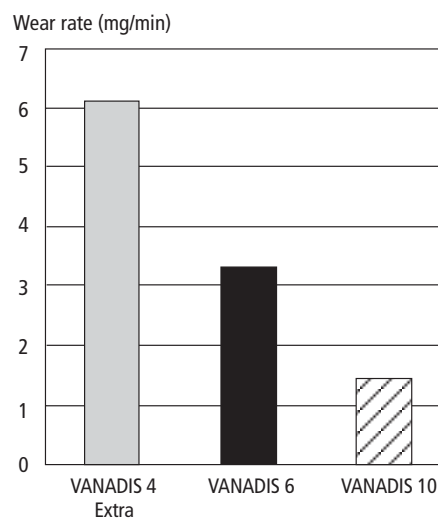

Electrical components blanked with a Vanadis 6 punch.

Heat treatment

SOFT ANNEALING

Protect the steel and heat through to 900°C (1650°F). Then cool in the furnace at 10°C (20°F) per hour to 750°C (1380°F), then freely in air.

STRESS RELIEVING

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

HARDENING

Pre-heating temperature: Normally two pre-heating steps 600–650°C (1110–1200°F) and 900–950°C (1650–1740°F).

Austenitizing temperature: 1000–1100°C (1830–2010°F). Normally 1050°C (1920°F).

Holding time: 30 min. below 1100°C (2010°F), 15 min. above 1100°C (2010°F).

Protect the tool against decarburization and oxidation during hardening.

QUENCHING MEDIA


- High speed gas/circulating atmosphere
- Vacuum (high speed gas with sufficient positive pressure), preferably at least 4–5 bar
- Martempering bath or fluidized bed at 500–550°C (930–1020°F)
- Martempering bath or fluidized bed at approx. 200–350°C (390–660°F).

Note 1: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

Note 2: In order to obtain the optimum properties for the tool, the cooling rate should be as fast as is concurrent with acceptable distortion.

Note 3: Tools with sections >50 mm (2") should be quenched in sufficient gas pressure and speed. Quenching in still air will result in loss of hardness.

Hardness and retained austenite as functions of austenitizing temperature

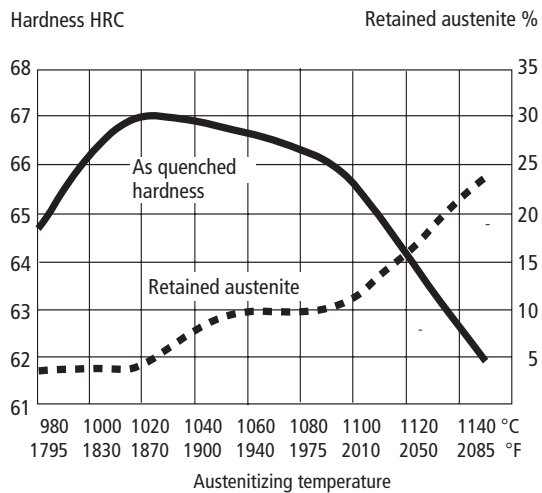

TEMPERING

The tempering temperature can be selected according to the hardness required by referencing the tempering graphs on the next page. Temper minimum twice with intermediate cooling to room temperature.

The lowest tempering temperature which should be used is 180°C (360°F). This temperature should only be used for small and uncomplicated tools.



For medium to large size and more complicated tools a temperature of 250°C (480°F) or higher should be used. When performing a high temperature temper, a temperature to the right of the secondary hardening peak should be chosen.

At a hardening temperature of 1100°C (2010°F) or higher Vanadis 6 must be tempered three times (holding time 1 hour) at minimum 525°C (980°F) in order to reduce the amount of retained austenite. Otherwise the minimum holding time at temperature is 2 hours.



Raufoss Teknologi AS, Verktøysfabriken, Norway.

Tempering graphs

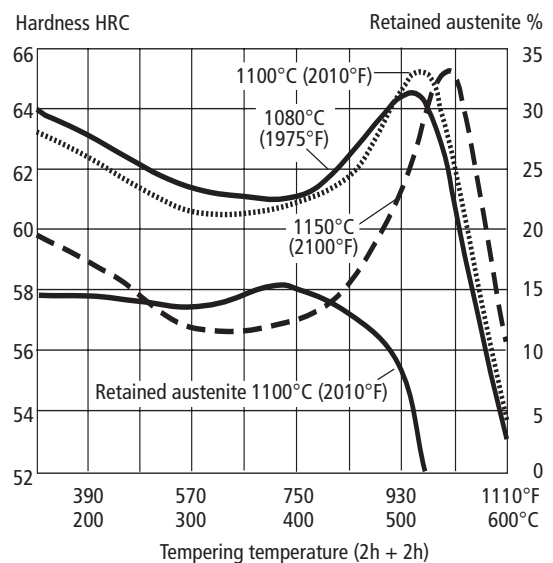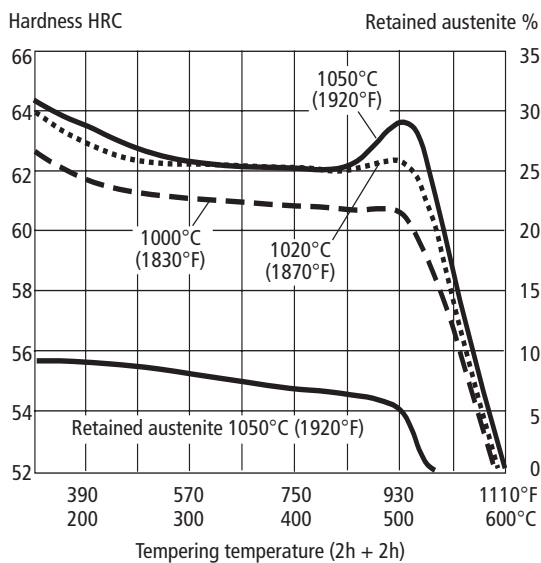

Tempering at high temperature after deep cooling (sub-zero cooling)

The tempering temperature should be lowered 25°C (50°F) in order to get the desired hardness when a high temperature temper is performed.


DIMENSIONAL CHANGES

The dimensional changes have been measured after austenitizing at 1050°C/30 min. (1920°F/30 min.) followed by gas quenching in a cold chamber vacuum furnace.

Specimen size: 65 x 65 x 65 mm (2,5" x 2,5" x 2,5")

Austenitizing temperature 1050°C (1920°F)

Dimensional changes %

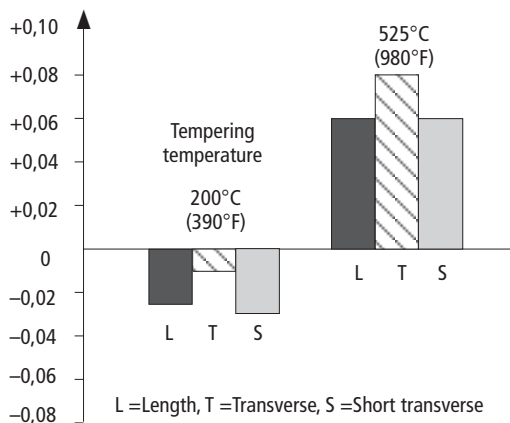


SUB-ZERO TREATMENT

Pieces requiring maximum dimensional stability can be sub-zero treated as follows:

Immediately after quenching the piece should be sub-zero treated to between -70 and -80°C (-95 to -110°F), soaking time 1-3 hours, followed by tempering. The tempering temperature should be lowered 25°C (50°F) in order to get the desired hardness when a high temperature temper is performed. Sub-zero treatment will give a hardness increase of ~1 HRC. Avoid intricate shapes as there will be risk of cracking.


For the highest demands of dimensional stability sub-zero cooling in liquid nitrogen is recommended after quenching and each tempering.

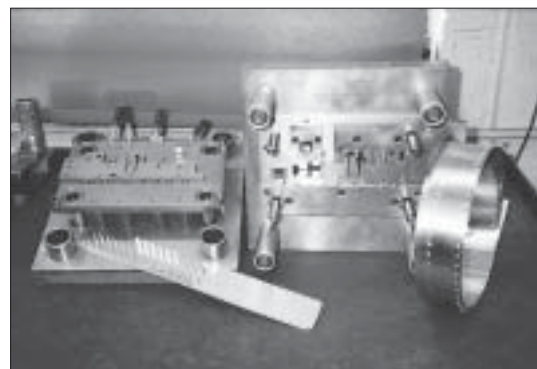

Parts blanked in a Vanadis 6 tool from Allenvale Tools & Production Ltd., Great Britain.


CCT-graph

Austenitizing temperature 1050°C (1920°F). Holding time 30 minutes.

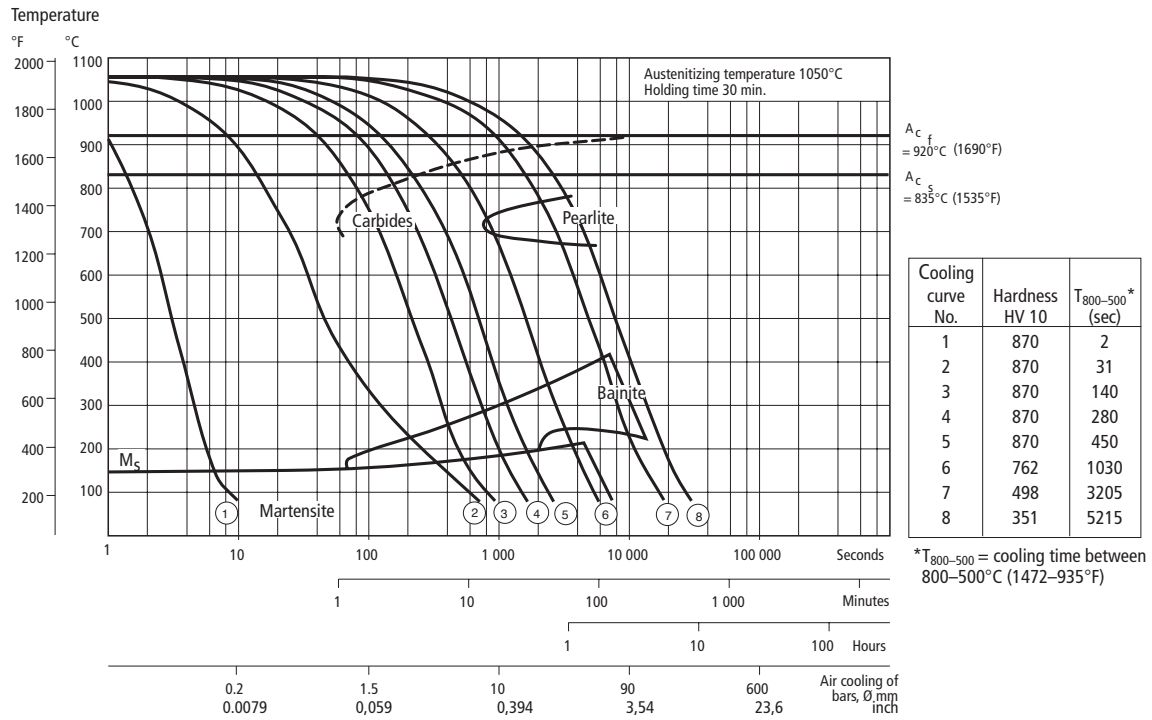

TTT-graph

Austenitizing temperature 1050°C (1920°F). Holding time 30 minutes.

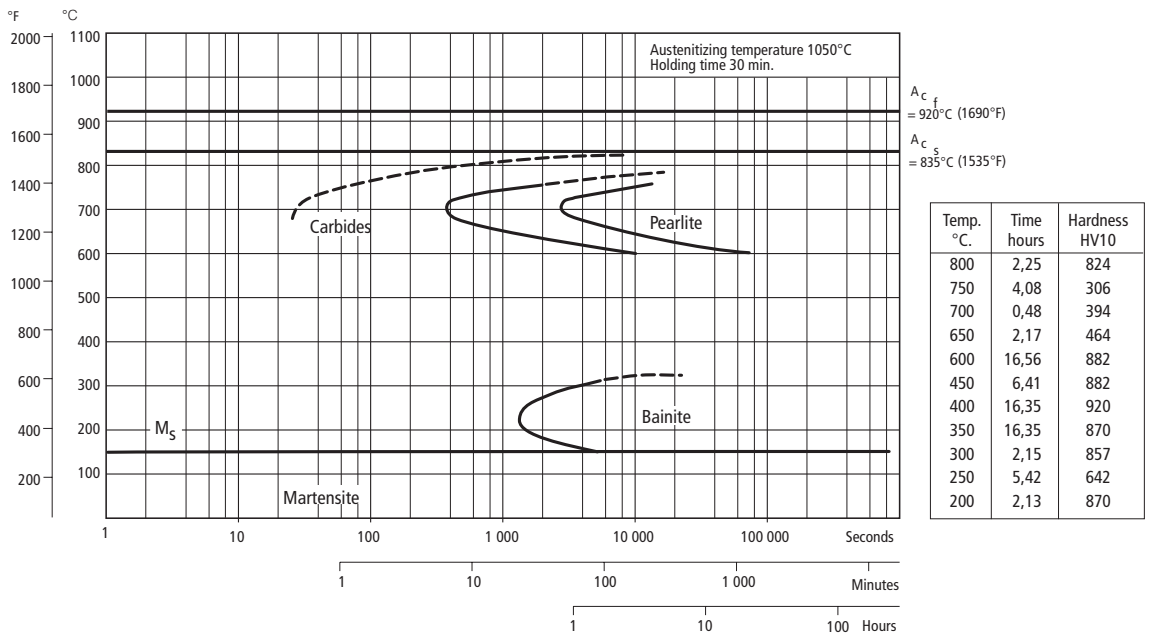

Surface treatment

Some cold work tool steels are given a surface treatment in order to reduce friction and increase wear resistance. The most commonly used treatments are nitriding and surface coating with wear resistant layers produced via PVD or CVD.

The high hardness and toughness together with a good dimensional stability makes Vanadis 6 ideal as a substrate steel for various surface coatings.

NITRIDING AND NITROCARBURIZING

Nitriding and nitrocarburizing result in a hard surface layer which is very resistant to wear and galling.


The surface hardness after nitriding is approximately 1250 HV_{0,2 kg}. The thickness of the layer should be chosen carefully, considering the high content of alloying elements, to suit the application in question.

PVD

Physical vapor deposition, PVD, is a method of applying a wear-resistant coating at temperatures between 200–500°C (390–930°F).

CVD

Chemical vapor deposition, CVD, is used for applying wear-resistant surface coatings at a temperature of around 1000°C (1830°F). It is recommended that the tools should be separately hardened and tempered in a vacuum furnace after surface treatment.

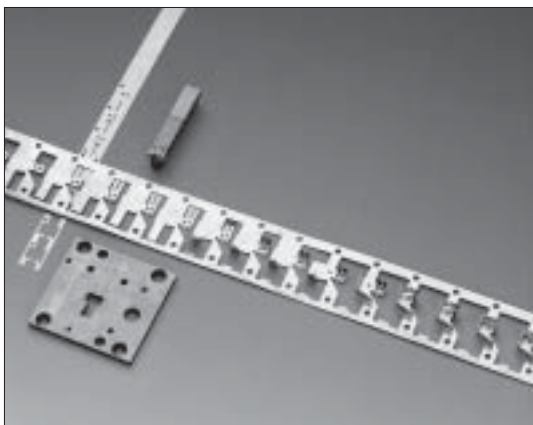

Blanked parts. Punch in Vanadis 6, die in Vanadis 10.

Machining recommendations

The cutting data below, valid for Vanadis 6 in soft annealed condition, are to be considered as guiding values which must be adapted to existing local conditions.

TURNING

Cutting data parameters	Turning with carbide		Turning with HSS Fine turning
	Rough turning	Fine turning	
Cutting speed (v_c) m/min. f.p.m.	70–100 230–330	100–120 230–395	8–10 23–33
Feed (f) mm/r i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,012
Depth of cut (a_p) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08	0,5–3 0,02–0,12
Carbide designation ISO US	K20* C3* Coated carbide	K15* C3* Coated carbide	–

* Use a wear resistance Al_2O_3 coated carbide grade

DRILLING

High speed steel twist drill

Drill diameter		Cutting speed (v_c)		Feed (f)	
mm	inch	m/min	f.p.m.	mm/r	i.p.r.
– 5	–3/16	8–10*	26–33*	0,05–0,15	0,002–0,006
5–10	3/16–3/8	8–10*	26–33*	0,15–0,20	0,006–0,008
10–15	3/8–5/8	8–10*	26–33*	0,20–0,25	0,008–0,010
15–20	5/8–3/4	8–10*	26–33*	0,25–0,35	0,010–0,014

* For coated HSS drills $v_c = 14–16$ m/min. (50–52 f.p.m.).

Carbide drill

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Brazed carbide ¹⁾
Cutting speed (v_c) m/min. f.p.m.	90–120 300–395	50–70 164–230	25–35 82–115
Feed (f) mm/r i.p.r.	0,05–0,25 ²⁾ 0,002–0,01 ²⁾	0,10–0,25 ²⁾ 0,004–0,01 ²⁾	0,15–0,25 ²⁾ 0,006–0,01 ²⁾

¹⁾ Drills with internal cooling channels and a brazed carbide tip.

²⁾ Depending on drill diameter.

MILLING

Face and square shoulder milling

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v_c) m/min. f.p.m.	40–70 130–230	70–100 230–330
Feed (f_z) mm/tooth in/tooth	0,2–0,4 0,008–0,016	0,1–0,2 0,004–0,008
Depth of cut (a_p) mm inch	2–4 0,08–0,16	1–2 0,04–0,08
Carbide designation ISO US	K20* C3* Coated carbide	K15* C3* Coated carbide

* Use a wear resistance Al_2O_3 coated carbide grade

End milling

Cutting data parameters	Type of milling		
	Solid carbide	Carbide indexable insert	High speed steel
Cutting speed (v_c) m/min. f.p.m.	35–45 115–148	70–90 200–260	5–8 ¹⁾ 16–26 ¹⁾
Feed (f_z) mm/tooth in/tooth	0,01–0,2 ²⁾ 0,0004–0,008 ²⁾	0,06–0,2 ²⁾ 0,002–0,008 ²⁾	0,01–0,30 ²⁾ 0,0004–0,012 ²⁾
Carbide designation ISO US	–	K15 ³⁾ C3 ³⁾	–

¹⁾ For coated HSS end mill $v_c = 12–16$ m/min. (39–52 f.p.m.).

²⁾ Depending on radial depth of cut and cutter diameter.

³⁾ Use a wear resistance Al_2O_3 coated carbide grade

GRINDING

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication "Grinding of Tool Steel".

Wheel recommendation

Type of grinding	Soft annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	B151 R50 B3 ¹⁾ A 46 GV
Face grinding segments	A 36 GV	A 46 GV
Cylindrical grinding	A 60 KV	B151 R50 B3 ¹⁾ A 60 JV
Internal grinding	A 60 JV	B151 R75 B3 ¹⁾ A 60 IV
Profile grinding	A 100 IV	B126 R100 B6 ¹⁾ A 100 JV

¹⁾ If possible use CBN wheels for this application

Electrical-discharge machining–EDM

If EDM is performed in the hardened and tempered condition, finish with “fine-sparking”, i.e. low current, high frequency.

For optimal performance the EDM’d surface should then be ground/polished and the tool retempered at approx. 25°C (50°F) lower than the original tempering temperature.

When EDM’ing larger sizes or complicated shapes Vanadis 6 should be tempered at high temperatures, above 500°C (930°F).

Further information

Please, contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

Relative comparison of Uddeholm cold work tool steel

MATERIAL PROPERTIES AND RESISTANCE TO FAILURE MECHANISMS

Uddeholm grade	Hardness/ Resistance to plastic deformation	Machinability	Grindability	Dimension stability	Resistance to		Fatigue cracking resistance	
					Abrasive wear	Adhesive wear	Ductility/ resistance to chipping	Toughness/ gross cracking
ARNE	█	█	█	█	█	█	█	█
CALMAX	█	█	█	█	█	█	█	█
CALDIE	█	█	█	█	█	█	█	█
RIGOR	█	█	█	█	█	█	█	█
SLEIPNER	█	█	█	█	█	█	█	█
SVERKER 21	█	█	█	█	█	█	█	█
SVERKER 3	█	█	█	█	█	█	█	█
VANADIS 4 Extra	█	█	█	█	█	█	█	█
VANADIS 6	█	█	█	█	█	█	█	█
VANADIS 10	█	█	█	█	█	█	█	█
VANADIS 23	█	█	█	█	█	█	█	█
VANADIS 30	█	█	█	█	█	█	█	█
VANADIS 60	█	█	█	█	█	█	█	█
AISI M:2	█	█	█	█	█	█	█	█

UDDEHOLM EUROPE

AUSTRIA

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

BELGIUM

UDDEHOLM N.V.
Waterstraat 4
B-9160 Lokeren
Telephone: +32 9 349 11 00
Telefax: +32 9 349 11 11

CROATIA

BOHLER UDDEHOLM Zagreb
d.o.o za trgovinu
Zitnjak b.b
10000 Zagreb
Telephone: +385 1 2459 301
Telefax: +385 1 2406 790

CZECHIA

BOHLER UDDEHOLM CZ s.r.o.
Division Uddeholm
U silnice 949
161 00 Praha 6 Ruzyne
Czech Republic
Telephone: +420 233 029 850,8
Telefax: +420 233 029 859

DENMARK

UDDEHOLM A/S
Kokmose 8, Bramdrupdam
DK-6000 Kolding
Telephone: +45 75 51 70 66
Telefax: +45 75 51 70 44

ESTONIA

UDDEHOLM TOOLING ESTI OÜ
Silikatsiidi 7
EE-11216 Tallinn, Estonia
Telephone: +372 655 9180
Telefax: +372 655 9181

FINLAND

OY UDDEHOLM AB
Ritakuja 1, PL 57,
FIN-01741 VANTAA
Telephone: +358 9 290 490
Telefax: +358 9 2904 9249

FRANCE

UDDEHOLM S.A.
12 Rue Mercier, Z.I. de Mitry-Compan
F-77297 Mitry Mory Cedex
Telephone: +33 (0)1 60 93 80 10
Telefax: +33 (0)1 60 93 80 01

Branch office

UDDEHOLM S.A.
77bis, rue de Vesoul
La Nef aux Métiers
F-25000 Besançon
Telephone: +33 381 53 12 19
Telefax: +33 381 53 13 20

GERMANY

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

Branch offices

UDDEHOLM
Falkenstraße 21
D-65812 Bad Soden/TS.
Telephone: +49 6196 659 60
Telefax: +49 6196 659 625

UDDEHOLM

Albstraße 10
D-73765 Neuhausen
Telephone: +49 715 898 65-0
Telefax: +49 715 898 65-25

GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED
European Business Park
Taylors Lane, Oldbury
West Midlands B69 2BN
Telephone: +44 121 552 55 11
Telefax: +44 121 544 29 11

Dublin Telephone: +353 1 45 14 01

GREECE

UDDEHOLM STEEL TRADING
COMPANY
20, Athinon Street
G-Piraeus 18540
Telephone: +30 2 10 41 72 109/41 29 820
Telefax: +30 2 10 41 72 767

Agency

SKLERO S.A.
Steel Trading Comp. and
Hardening Shop
Frixou 11/Nikif. Ouranou
G-54627 Thessaloniki
Telephone: +30 31 51 46 77
Telefax +30 31 54 12 50

SKLERO S.A.

Heat Treatment and Trading of Steel
Uddeholm Tool Steels
Industrial Area of Thessaloniki
P.O. Box 1123
G-57022 Sindos, Thessaloniki
Telephone: +30 23 10 79 76 46
Telefax: +30 23 10 79 76 78

HUNGARY

UDDEHOLM TOOLING/BOK
Dunaharaszti, Jedlik Ányos út 25
H-2331 Dunaharaszti 1.Pf. 110
Telephone/Telefax: +36 24 492 690

ITALY

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

LATVIA

UDDEHOLM TOOLING AB
Piedrujas street 7
LV-1037 Riga, Latvia
Telephone: +371 7 701 983, -981, -982
Telefax: +371 7 147 373

LITHUANIA

UDDEHOLM TOOLING AB
BE PLIENAS IR METALAI
T. Masiulio 18b
LT-52459 Kaunas
Telephone: +370 37 370613, -669
Telefax: +370 37 370300

THE NETHERLANDS

UDDEHOLM B.V.
Isolatorweg 30
NL-1014 AS Amsterdam
Telephone: +31 20 581 71 11
Telefax: +31 20 684 86 13

NORWAY

UDDEHOLM A/S
Jernkroken 18
Postboks 85, Kalbakken
N-0902 Oslo
Telephone: +47 22 91 80 00
Telefax: +47 22 91 80 01

POLAND

INTER STAL CENTRUM
Sp. z o.o./Co. Ltd.
ul. Kolejowa 291, Dziekanów Polski
PL-05-092 Lomianki
Telephone: +48 22 429 2260
Telefax: +48 22 429 2266

PORTUGAL

F RAMADA Aços e Industrias S.A.
P.O. Box 10
P-3881 Ovar Codex
Telephone: +351 56 58 61 11
Telefax: +351 56 58 60 24

ROMANIA

BÖHLER Romania SRL
Uddeholm Branch
Str. Atomistilor Nr 14A
077125 Magurele Jud Ilfov
Telephone: +40 214 575007
Telefax: +40 214 574212

RUSSIA

UDDEHOLM TOOLING CIS
25 A Bolshoy pr PS
197198 St. Petersburg
Telephone: +7 812 233 9683
Telefax: +7 812 232 4679

SLOVAKIA

UDDEHOLM Slovakia
Nástrojové ocele, s.r.o
KRÁCINY 2
036 01 Martin
Telephone: +421 842 4 300 823
Telefax: +421 842 4 224 028

SLOVENIA

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

SPAIN

UDDEHOLM
Guifré 690-692
E-08918 Badalona, Barcelona
Telephone: +34 93 460 1227
Telefax: +34 93 460 0558

Branch office

UDDEHOLM
Barrio San Martin de Arteaga, 132
Pol.Ind. Torrelarragoiti
E-48170 Zamudio
(Bizkaia)
Telephone: +34 94 452 13 03
Telefax: +34 94 452 13 58

SWEDEN

UDDEHOLM TOOLING
SVENSKA AB
Aminogatan 25
SE-431 53 Mölndal
Telephone: +46 31 67 98 50
Telefax: +46 31 27 02 94

SWITZERLAND

HERTSCH & CIE AG
General Wille Strasse 19
CH-8027 Zürich
Telephone: +41 44 208 16 66
Telefax: +41 44 201 46 15

UDDEHOLM NORTH AMERICA

USA

UDDEHOLM
4902 Tollview Drive
Rolling Meadows, IL 60008
Sales Phone: +1 800 638 2520
Sales Fax: +1 630 350 0880

Region East Warehouse
UDDEHOLM – Shrewsbury, MA

Region Central Warehouse
UDDEHOLM – Wood Dale, IL

Region West Warehouse
UDDEHOLM – Santa Fe Springs, CA

CANADA

UDDEHOLM
2595 Meadowvale Blvd.
Mississauga, ON L5N 7Y3
Telephone: +1 905 812 9440
Telefax: +1 905 812 8658

Branch Warehouses

UDDEHOLM – St. Laurent, QC
UDDEHOLM – New Westminster, BC

Heat Treating

THERMO-TECH – Mississauga, ON

MEXICO

ACEROS BOHLER UDDEHOLM,
S.A. de C.V.
Calle 8 No 2, Letra "C"
Fraccionamiento Industrial Alce Blanco
C.P. 52787 Naucalpan de Juarez
Estado de Mexico
Telephone: +52 55 9172 0242
Telefax: +52 55 5576 6837

UDDEHOLM

Derdo de Tejada No.542
Colonia Las Villas
66420 San Nicolas de Los Garza, N.L.
Telephone: +52 8-352 5239
Telefax: +52 8-352 5356

UDDEHOLM SOUTH AMERICA

ARGENTINA

UDDEHOLM S.A
Mozart 40
1619-Centro Industrial Garin
Garin-Prov. Buenos Aires
Telephone: +54 332 744 4440
Telefax: +54 332 745 3222

BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.
Estrada Yae Massumoto, 353
CEP 09842-160
Sao Bernardo do Campo - SP Brazil
Telephone: +55 11 4393 4560, -4554
Telefax: +55 11 4393 4561

UDDEHOLM SOUTH AFRICA

UDDEHOLM Africa (Pty) Ltd.
P.O. Box 539
ZA-1600 Isando/Johannesburg
Telephone: +27 11-974 2781
Telefax: +27 11-392 2486

UDDEHOLM AUSTRALIA

BOHLER-UDDEHOLM Australia
129-135 McCredie Road
Guildford NSW 2161
Private Bag 14
Telephone: +61 2 9681 3100
Telefax: +61 2 9632 6161

Branch offices

Sydney, Melbourne, Adelaide,
Brisbane, Perth, Newcastle,
Launceston, Albury, Townsville

ASSAB

ASSAB INTERNATIONAL

Skytteholmsvägen 2
P O Box 42
SE-171 11 Solna
Sweden
Telephone: +46 8 564 616 70
Telefax: +46 8 25 02 37

Subsidiaries

India, Iran, Turkey, United Arab
Emirates, Saudi Arabia

Distributors in

Africa, Latin America, Middle East

ASSAB PACIFIC

ASSAB Pacific Pte. Ltd
171, Chin Swee Road
No. 07-02, San Centre
Singapore 169877
Telephone: +65 534 56 00
Telefax: +65 534 06 55

Subsidiaries

China, Hong Kong, Indonesia, Japan,
Korea, Malaysia, Philippine Islands,
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

